

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

Program: NASA GODDARD		Report Date: 12/31/2001
Generic Part No. IRLML5103A	Part Description: 30V, 0.6-Ω P-Channel MOSFET	Manufacturer: International Rectifier Corp.
Package Type: Micro 3	Date Code: 0034	Package Markings 1B 1C
Detailed Test Specification: IRLML5103 TID Test Plan	General Test Requirement: None	Performance Specification IRLM5103 Specification by IR
Serial Number: 1, 2, 3, 4, 5, 6, 7, 8, 9, & 10 (S/N assigned randomly)		Radiation Test Results See Appendix B, C, D, & E

1.0 Summary.

NAVSEA Crane was tasked to evaluate the total ionizing dose (TID) performance of a P-channel 30-V, 0.6-Ohm MOSFET, the IRLML5103A manufactured by International Rectifier, to conditions specified under the IRLML5103 TID Test Plan drafted by Christian Poivey, NASA-GSFC, Code 561, Greenbelt MD 20771. Specifically, NAVSEA Crane performed these tests:

- a.) Electrical Measurements (I_{DSS} , $R_{DS(ON)}$, and $V_{GS(TH)}$); Total Dose Tests at 2.5, 5, 10, 20, 30, and 50 krd(Si) using a dose rate < 1 rd(Si)/s under a bias of $V_D = V_S = 5V$ and $V_G = 0V$; and Post Radiation Anneal Test for 168 hrs @ 25 °C using the same radiation fixture and biases. Electrical Measurements were performed initially and after each radiation step and following the Anneal Test.

Test results indicate the following that I_{DSS} increased to a maximum of 240 pA at 50 krds and to 555 pA after the anneal; R_{DSON} increased to a maximum of 55 ohms at 50 krds and to 54 ohms after the anneal; and V_{GSTH} increased to a maximum of -3.15 V at 50 krds and to -3.14 after the anneal.

Detailed radiation responses are provided in Appendix B, C, D, and E.

2.0 Applicable Documents.

The major applicable documents, used to perform the TID tests, are listed here:

- a) IRLML5103 TID Test Plan Specific Test Plan by NASA
- b) IRLML5103 Specification Performance Specification of IRLML5103 by IR (8/25/97)
- c) MIL-STD-750D Test Methods for Semiconductor Devices
 - Method 1019.4 Steady State Total Dose Irradiation Procedure
 - Method 3400 Conditions for Measurement of MOSFET Parameters
 - 3411.1 Gate Reverse Current (I_{G_OFF})
 - 3415.1 Drain Reverse Current (I_{D_OFF})
 - 3421.1 Static Drain to Source On Resistance (R_{DS_ON})
 - 3403.1 Gate to source Voltage (V_{GS_OFF})
- e) ASTM Standard E668 Standard Practice for the Application of Thermoluminescence Dosimetry (TLD) Systems for Determining Absorbed Dose in Radiation Hardness Testing of Electronic Devices - Annual Book of ASTM Standards, Vol. 12.02: Nuclear (II), Solar, and Geothermal Energy, American Society for Testing and Materials
- f) NAVSEA INST 4734.1 NAVSEA Metrology and Calibration Program
- g) DOD-HDBK-263 Handbook - Electrostatic discharge sensitive devices

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

3.0 Handling Precautions.

Handling precautions were observed to minimize electrostatic discharge (ESD).

4.0 Electrical Test.

Electrical measurements were performed using a Tektronix 370 curve tracer for $V_{GS(TH)}$ and $R_{DS(ON)}$ parameters and using an automated test system consisting of two Keithley 237 SMU's and a controller for the I_{DSS} parameter. Ten samples consisting of two controls and eight test samples were characterized. These electrical test parameters were measured:

PARAMETER	CONDITION	PARAMETER	LIMIT
Zero Gate Voltage Drain Current	$V_{DS} = -24 \text{ V}$ $V_{GS} = 0 \text{ V}$	I_{DSS}	$< -1 \mu\text{A}$
Static Drain-Source On Resistance	$I_{DS} = -0.3 \text{ A}$ $V_{GS} = -4.5 \text{ V}$	R_{DS_ON}	$< 1.0 \Omega$
Gate Threshold Voltage	$I_{DS} = -250 \mu\text{A}$ $V_{DS} = V_{GS}$	$V_{GS(TH)}$	$> -1 \text{ V}$

Note: Appendix A provides a summary of a visual inspection of the test samples.
Appendix B provides a summary of the initial pre-rad electrical test measurements.
Appendix C provides a summary of the post-rad electrical test measurements.
Appendix D provides a summary of the post-anneal electrical test measurements.
Appendix E provides a graphical summary of the electrical test parameters.

4.1 Test Conditions.

Test conditions were performed as specified by the applicable documents of 2.0 (specifically, the IRLML5103 TID Test Plan). All electrical measurements were performed at an ambient room temperature of $22 \text{ }^\circ\text{C} \pm 5^\circ\text{C}$ and recorded for each test sequence.

5.0 Total Ionizing Dose (TID) Test.

Total ionizing dose tests were performed at the NAVSEA Crane Co-60 test facility using a J. L. Shepherd and Associates Model 81-22 Irradiator with a Model 484 Radiation Tunnel and Interlock Door Assembly. Test samples were placed inside a Pb/Al container to minimize dose enhancement effects caused by low-energy scattering. The desired dose rate is achieved by selecting different amounts of radioactivity and distance. For this test, the 8,000 curies source was used with the positioning table set at a distance of 670 mm.

5.1 Bias Circuit.

A custom bias board was designed and fabricated to perform the TID tests. The bias circuit conformed to the requirements of the test specification (see bias conditions - NASA IRLML5103 TID Test Plan). Figure 1 depicts the TID insitu bias circuit used for six of the eight test samples. The other two samples were biased with all leads common. Figure 2 shows the CAD layout of the TID bias board. Note that all eight test samples were exposed simultaneously.

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

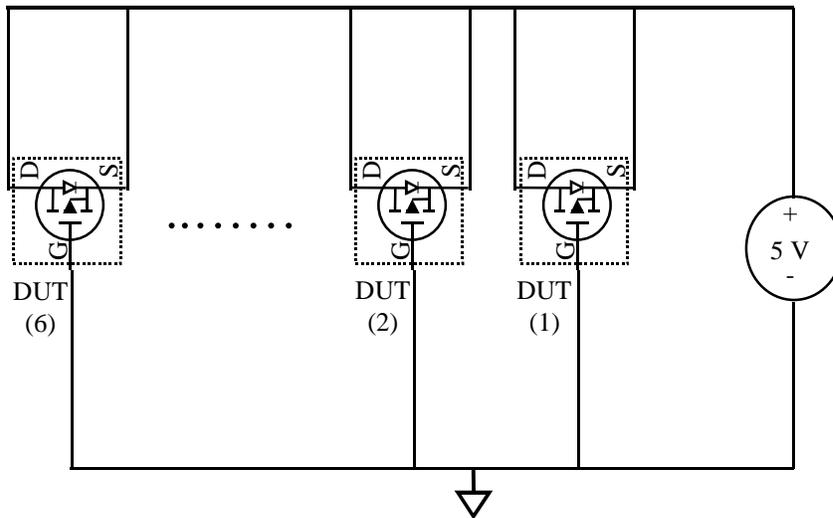


Figure 1. Insitu bias circuit used for TID test.

Top of Board
P-Channel MOSFET TID Board

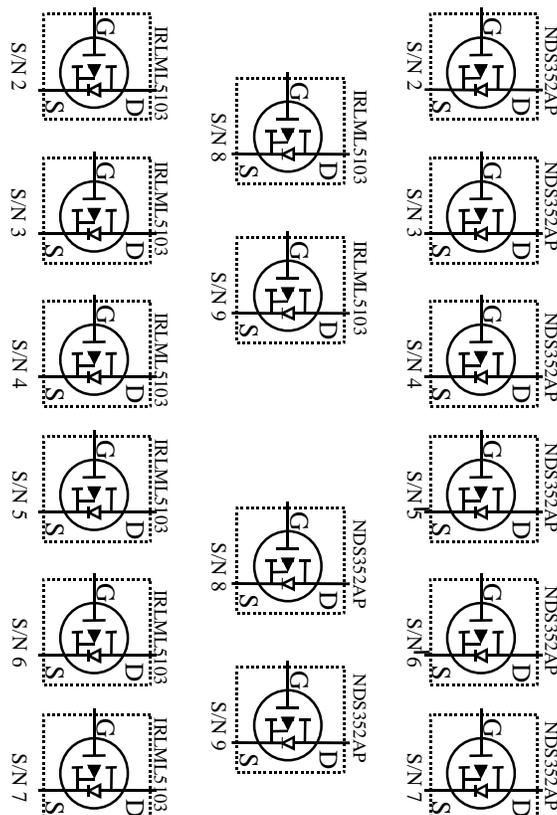


Figure 2. TID board layout of bias circuitry.

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

5.2 Dosimetry.

Dosimetry standard is described in 2.0(e). For total dose dosimetry, three ribbons were placed in a TLD holder and wrapped in a thin, (~0.001 inches) aluminum foil. The average reading of these three ribbons is used to determine the dose rate of the Co-60 source. For this test, TLDs were placed upon the top left socket, top right socket, bottom left socket, bottom right socket and the middle of all the sockets as depicted in Figure 3. Note this dosimetry was used for all subsequent tests. Table 2 provides a summary of the Co-60 Gamma Cell 220 source dosimetry.

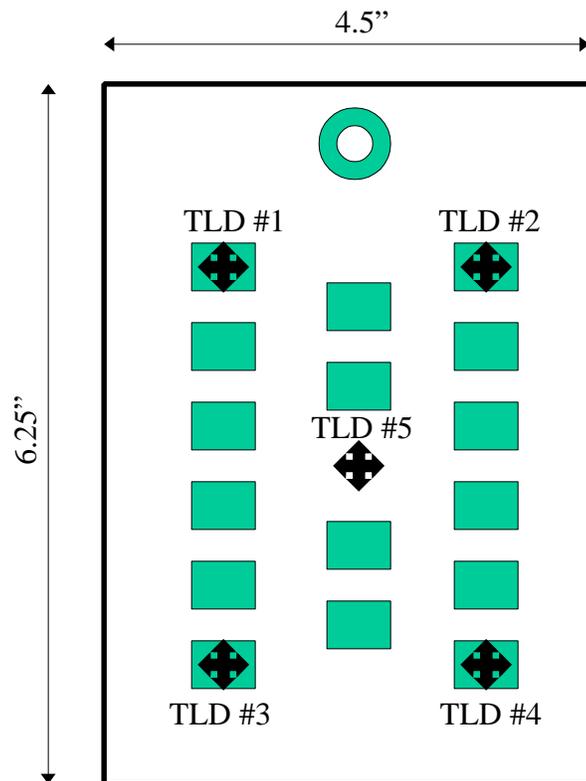


Figure 3. Pictorial Representation Showing TLD Placement.

Table 2. Verification of Co-60 Source

TLD Package	Slide Number	Avg. Dose Rd(CaF2)	Standard Deviation	Dose Rate [Rd(Si)/s]	Board Position
1	101	123.5	2.9%	0.8948	Top Left
2	102	124.2	0.6%	0.9000	Top Right
3	103	127.4	3.8%	0.9228	Bottom Left
4	104	119.7	1.4%	0.8677	Bottom Right
5	105	123.4	2.6%	0.8942	Middle
6	106	2489	1.6%	0.8861	Top Right

NAVSEA Crane Radiation Test Report

Report No: NSW C6054-IRLML5103-0001

Based upon the dosimetry, the dose rate was determined to be 0.89 rd(Si)/s. To validate the first radiation level (and to verify the dose rate), another TLD (top right corner) was placed upon the TID board above the top right socket. The exposure time was set for 2809 seconds ($0.89 \times 2,809 = 2,500$), resulting in an average TLD reading of 2,489 rd(Si).

Table 3 is a summary of the required exposure times to achieve radiation levels of 2.5, 5, 10, 20, 30, and 50 krd(Si) as required by the IRLML5103 TID Test Plan. Table 3 also provides the times to perform the electrical measurements between each exposure.

Table 3. Summary of Exposure and Electrical Test Times of TID Test

Total Dose Test Date	Exposure Start Time	Exposure Stop Time	Total Dose Rd(Si)	Electrical Test Start Time	Electrical Test Stop Time
12/18/2001	11:12 AM	11:59 AM	2,500	12:00 PM	12:38 PM
12/18/2001	12:40 PM	1:26 PM	5,000	1:28 PM	2:00 PM
12/18/2001	2:03 PM	3:38 PM	10,000	3:39 PM	4:11 PM
12/18/2001	4:15 PM	7:23 PM	20,000	7:25 PM	8:04 PM
12/18/2001	8:07 PM	11:16 PM	30,000	11:17 PM	11:53 PM
12/19/2001	12:08 AM	6:28 AM	50,000	6:37 AM	7:25 AM

5.3 Post-Radiation Anneal Test.

Upon completion of the last exposure (50 krd(Si)) and electrical characterization, samples were annealed for 168 hours at 25 °C under similar bias conditions. After annealing, the samples were electrically characterized again. This was specified in the IRLML5103 TID Test Plan.

NAVSEA Crane Radiation Test Report

Report No: NSW C6054-IRLML5103-0001

APPENDIX A. Visual Inspection Summary

Tagged S/N	Package Markings	Marking Verified	Comments
001	1B 1C	Yes	S/N Printed on DUT Card
002	1B 1C	Yes	S/N Printed on DUT Card
003	1B 1C	Yes	S/N Printed on DUT Card
004	1B 1C	Yes	S/N Printed on DUT Card
005	1B 1C	Yes	S/N Printed on DUT Card
006	1B 1C	Yes	S/N Printed on DUT Card
007	1B 1C	Yes	S/N Printed on DUT Card
008	1B 1C	Yes	S/N Printed on DUT Card
009	1B 1C	Yes	S/N Printed on DUT Card
010	1B 1C	Yes	S/N Printed on DUT Card

Note: Samples were mounted on a custom designed Device under test (DUT) card to facilitate handling and testing protocols. Serial numbers were randomly assigned and marked on each DUT card using a permanent marker.

Appendix B. Summary of Initial Electrical Test Data

Radiation Level - 0 rd(Si)				
S/N	I_{DSS} $V_{DS} = -24V$ $V_{GS} = 0 V$ (A)	$R_{DS(ON)}$ $I_{DS} = -0.3 A$ $V_{GS} = -4.5 V$ (Ohms)	$V_{GS(TH)}$ $V_{DS} = V_{GS}$ $I_{DS} = -250 mA$ (Volts)	Radiation Sample Description
001	3.50E-12	0.80	-1.88	Control
002	4.50E-12	0.77	-1.8	Biased
003	2.30E-11	0.77	-1.8	Biased
004	2.50E-10	0.80	-1.87	Biased
005	3.80E-12	0.78	-1.82	Biased
006	4.50E-12	0.76	-1.76	Biased
007	8.90E-12	0.80	-1.87	Biased
008	8.20E-12	0.76	-1.77	PINS COMMON
009	3.80E-12	0.81	-1.89	PINS COMMON
010	3.70E-12	0.80	-1.87	Control

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

Appendix C. Summary of Electrical Parameters After each Radiation Level

Radiation Level 2,500 rd(Si)				
S/N	I _{DSS} (A)	R _{DS(ON)} (Ohms)	V _{GS(TH)} (Volts)	Radiation Sample Description
001	3.40E-12	0.80	-1.88	Control
002	7.60E-12	0.79	-1.87	Biased
003	2.20E-11	0.79	-1.87	Biased
004	8.50E-11	0.82	-1.94	Biased
005	7.40E-12	0.80	-1.89	Biased
006	8.00E-12	0.78	-1.83	Biased
007	1.20E-11	0.82	-1.94	Biased
008	6.30E-12	0.77	-1.81	PINS COMMON
009	3.20E-12	0.82	-1.93	PINS COMMON
010	2.70E-12	0.80	-1.86	Control
Radiation Level 5,000 rd(Si)				
S/N	I _{DSS} (A)	R _{DS(ON)} (Ohms)	V _{GS(TH)} (Volts)	Radiation Sample Description
001	3.36E-12	0.80	-1.88	Control
002	1.79E-11	0.81	-1.94	Biased
003	3.45E-11	0.82	-1.94	Biased
004	1.13E-10	0.85	-2.01	Biased
005	1.85E-11	0.83	-1.96	Biased
006	1.98E-11	0.80	-1.89	Biased
007	2.53E-11	0.84	-2	Biased
008	9.00E-12	0.78	-1.85	PINS COMMON
009	5.50E-12	0.83	-1.97	PINS COMMON
010	3.00E-12	0.80	-1.86	Control
Radiation Level 10,000 rd(Si)				
S/N	I _{DSS} (A)	R _{DS(ON)} (Ohms)	V _{GS(TH)} (Volts)	Radiation Sample Description
001	3.50E-12	0.80	-1.88	Control
002	4.30E-11	0.86	-2.075	Biased
003	6.00E-11	0.87	-2.075	Biased
004	1.40E-10	0.91	-2.145	Biased
005	4.60E-11	0.88	-2.1	Biased
006	4.90E-11	0.85	-2.03	Biased
007	5.60E-11	0.89	-2.14	Biased
008	1.40E-11	0.80	-1.93	PINS COMMON
009	1.00E-11	0.85	-2.05	PINS COMMON
010	3.00E-12	0.80	-1.865	Control

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

Appendix C. Summary of Electrical Parameters After each Radiation Level (CONT.)

Radiation Level 20,000 rd(Si)				
S/N	I _{DSS} (A)	R _{DS(ON)} (Ohms)	V _{GS(TH)} (Volts)	Radiation Sample Description
001	3.20E-12	0.80	-1.88	Control
002	1.01E-10	1.02	-2.35	Biased
003	1.15E-10	1.03	-2.35	Biased
004	1.90E-10	1.09	-2.42	Biased
005	1.08E-10	1.04	-2.38	Biased
006	1.13E-10	0.99	-2.3	Biased
007	1.23E-10	1.07	-2.41	Biased
008	2.37E-11	0.84	-2.07	PINS COMMON
009	1.92E-11	0.90	-2.19	PINS COMMON
010	2.80E-12	0.80	-1.87	Control
Radiation Level 30,000 rd(Si)				
S/N	I _{DSS} (A)	R _{DS(ON)} (Ohms)	V _{GS(TH)} (Volts)	Radiation Sample Description
001	3.10E-12	0.80	-1.88	Control
002	1.18E-10	1.26	-2.605	Biased
003	1.31E-10	1.27	-2.605	Biased
004	2.05E-10	1.40	-2.675	Biased
005	1.25E-10	1.32	-2.63	Biased
006	1.31E-10	1.22	-2.55	Biased
007	1.49E-10	1.36	-2.66	Biased
008	3.80E-11	0.89	-2.19	PINS COMMON
009	3.20E-11	0.95	-2.31	PINS COMMON
010	2.80E-12	0.79	-1.865	Control
Radiation Level 50,000 rd(Si)				
S/N	I _{DSS} (A)	R _{DS(ON)} (Ohms)	V _{GS(TH)} (Volts)	Radiation Sample Description
001	2.90E-12	0.80	-1.88	Control
002	1.73E-10	22.10	-3.09	Biased
003	1.81E-10	22.20	-3.09	Biased
004	2.39E-10			Biased
005	1.87E-10	37.53	-3.11	Biased
006	1.89E-10	4.27	-3.03	Biased
007	2.15E-10	54.33	-3.14	Biased
008	6.30E-11	0.95	-2.39	PINS COMMON
009	5.60E-11	1.06	-2.51	PINS COMMON
010	2.60E-12	0.80	-1.86	Control

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

Appendix D. Summary of Electrical Tests After 168 hr Anneal


Anneal: 168 hours @ 25 °C - (Post-rad at 50,000 rd(Si))				
S/N	I_{DSS} $V_{DS} = -24V$ $V_{GS} = 0 V$ (A)	$R_{DS(ON)}$ $I_{DS} = -0.3 A$ $V_{GS} = -4.5 V$ (Ohms)	$V_{GS(TH)}$ $V_{DS} = V_{GS}$ $I_{DS} = -250 mA$ (Volts)	Radiation Sample Description
001	4.00E-12	0.79	-1.890	Control
002	5.55E-10	19.03	-3.090	Biased
003	4.90E-10	19.00	-3.080	Biased
004	*	*	*	Biased
005	4.95E-10	34.53	-3.120	Biased
006	5.08E-10	4.03	-3.030	Biased
007	5.50E-10	53.33	-3.140	Biased
008	1.67E-10	0.98	-2.390	PINS COMMON
009	1.50E-10	1.06	-2.510	PINS COMMON
010	3.00E-12	0.79	-1.870	Control

* Note: Electrical test parameter changed during characterization - most likely induced by internal heating during test causing the device to self anneal.

NAVSEA Crane Radiation Test Report


Report No: NSWC C6054-IRLML5103-0001

Appendix E. Graphical Summary of Electrical Tests Results

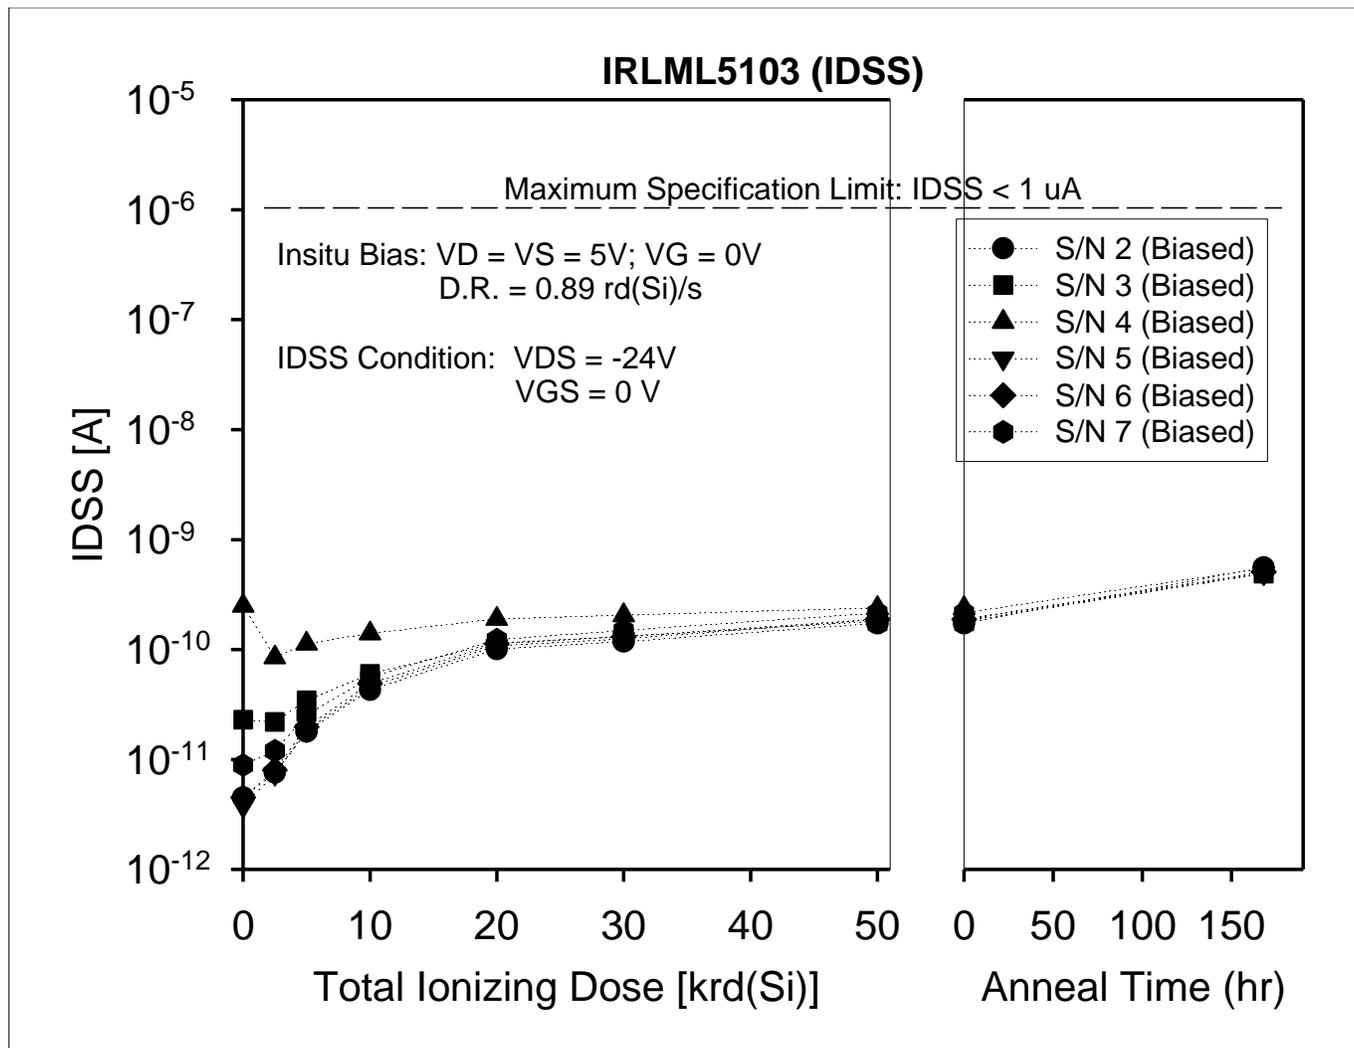


NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

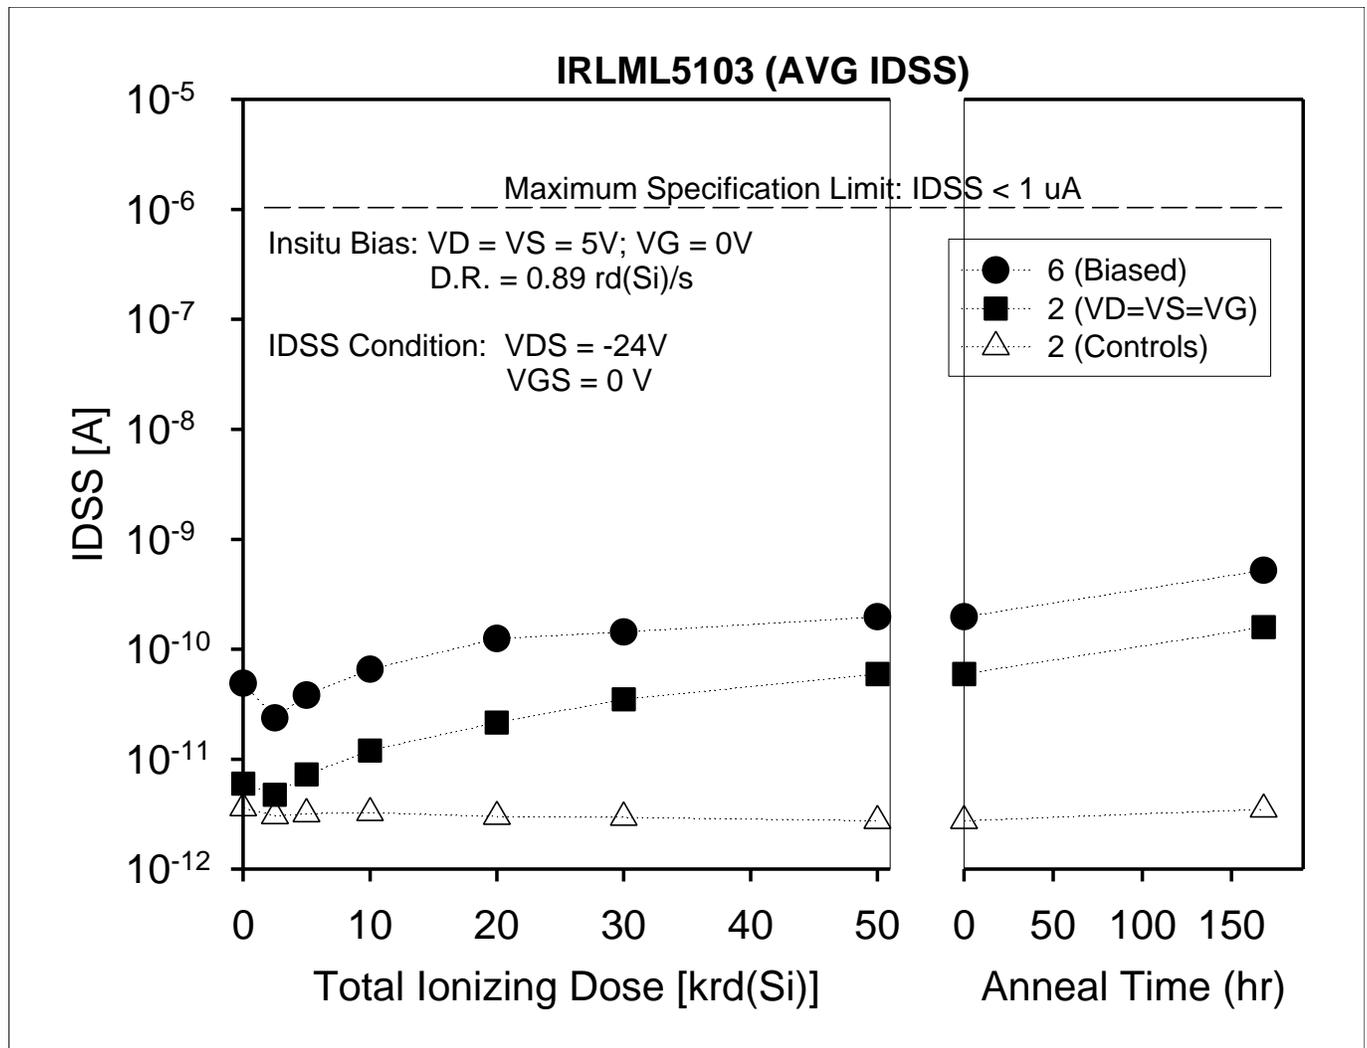


NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

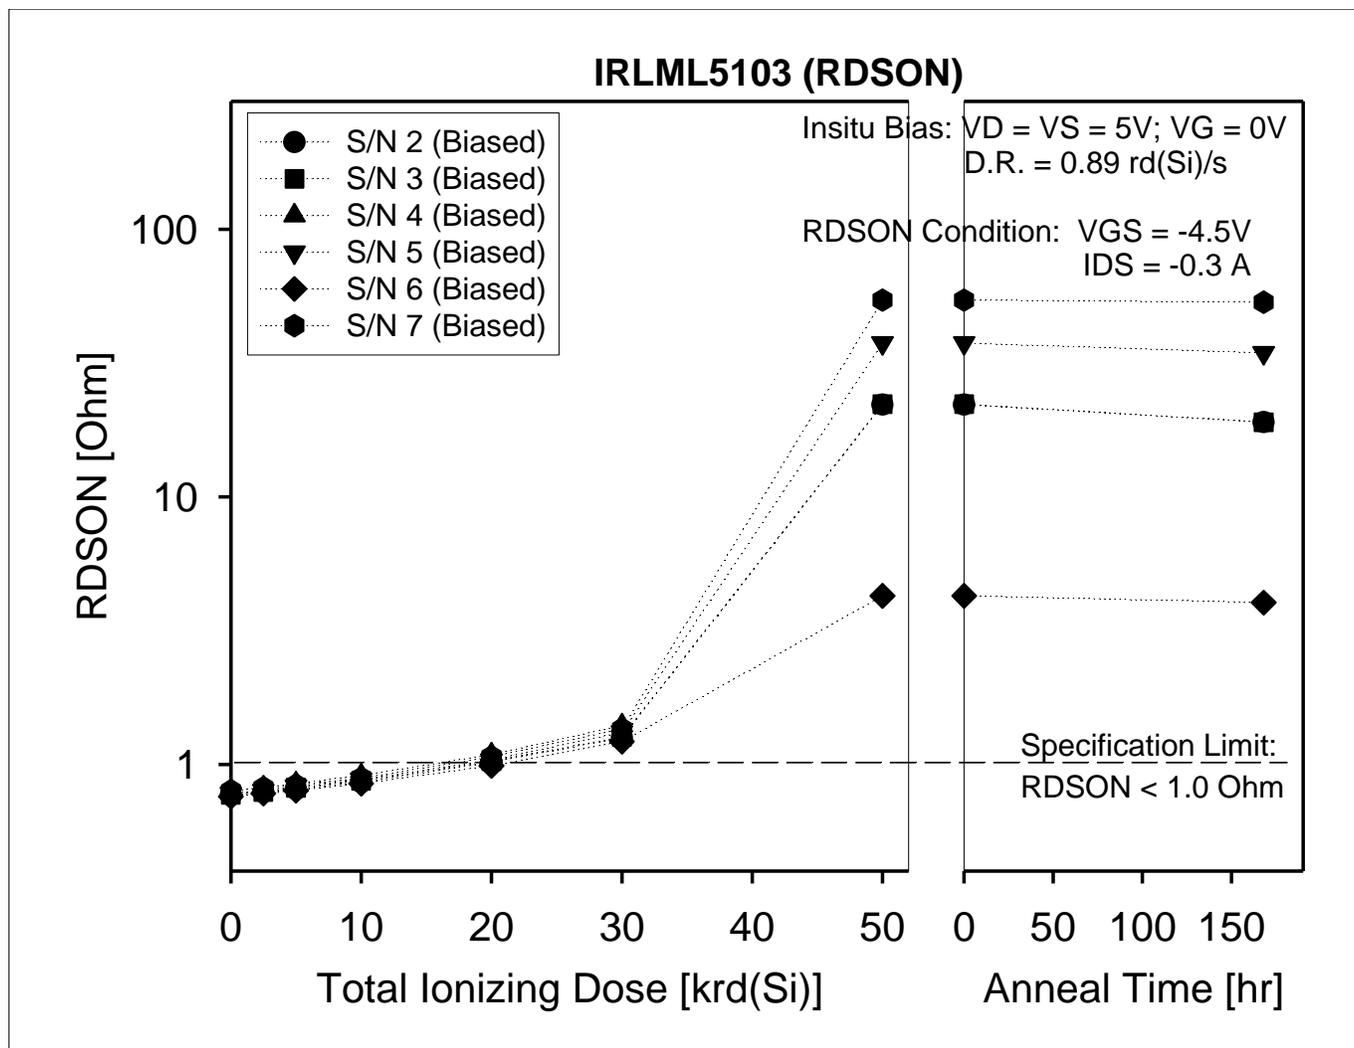

NAVSEA Crane Radiation Test Report


Report No: NSW C6054-IRLML5103-0001

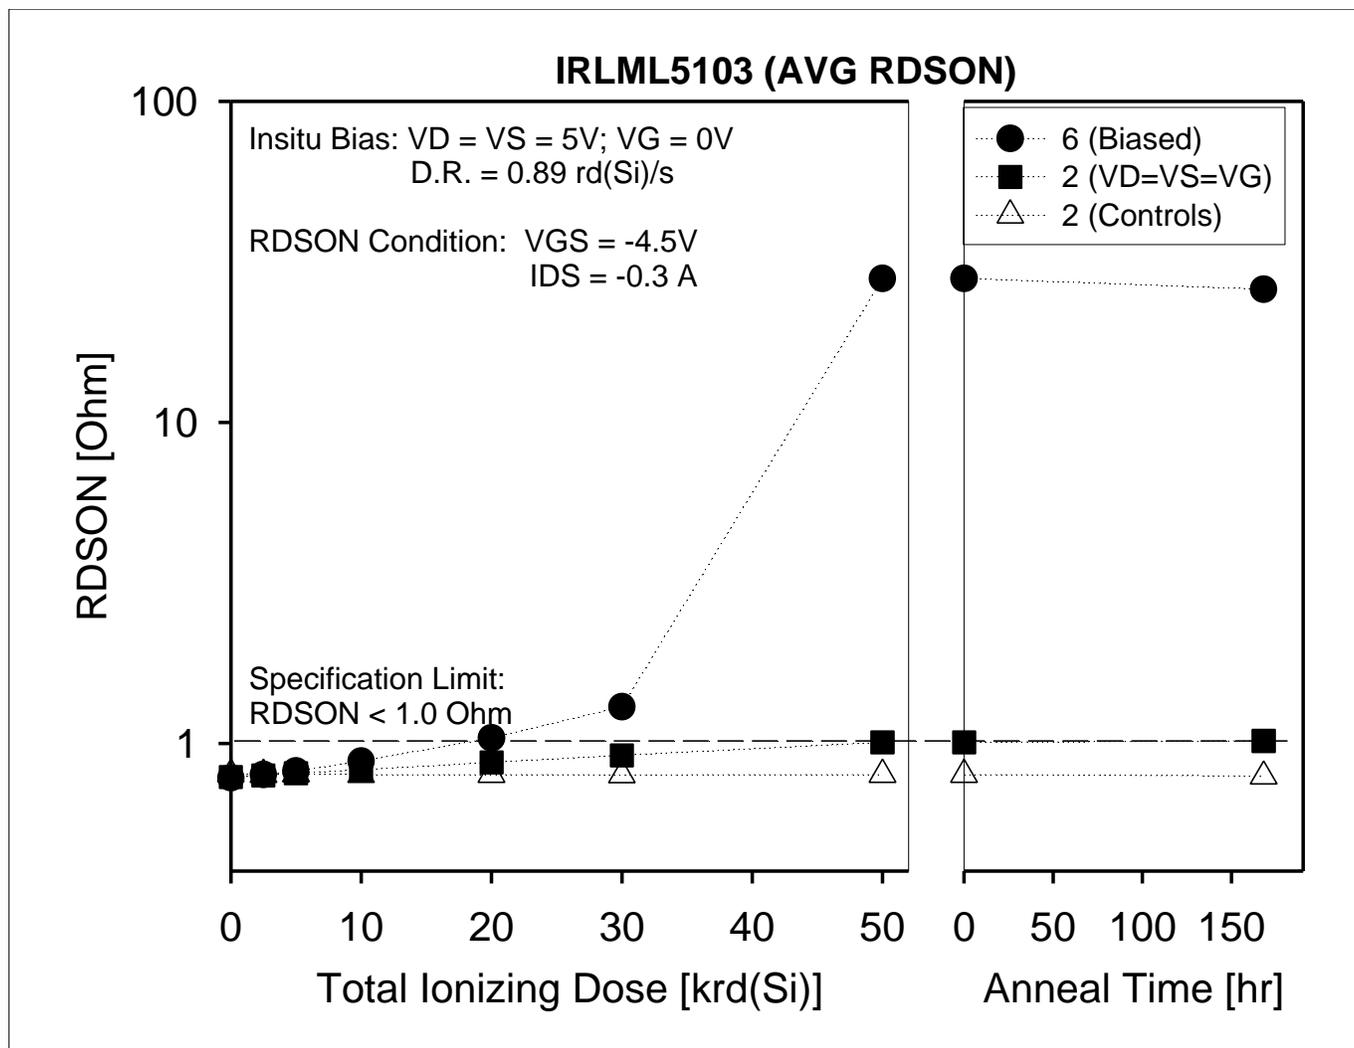

NAVSEA Crane Radiation Test Report


Report No: NSWC C6054-IRLML5103-0001

IRLML5103 (VTH)

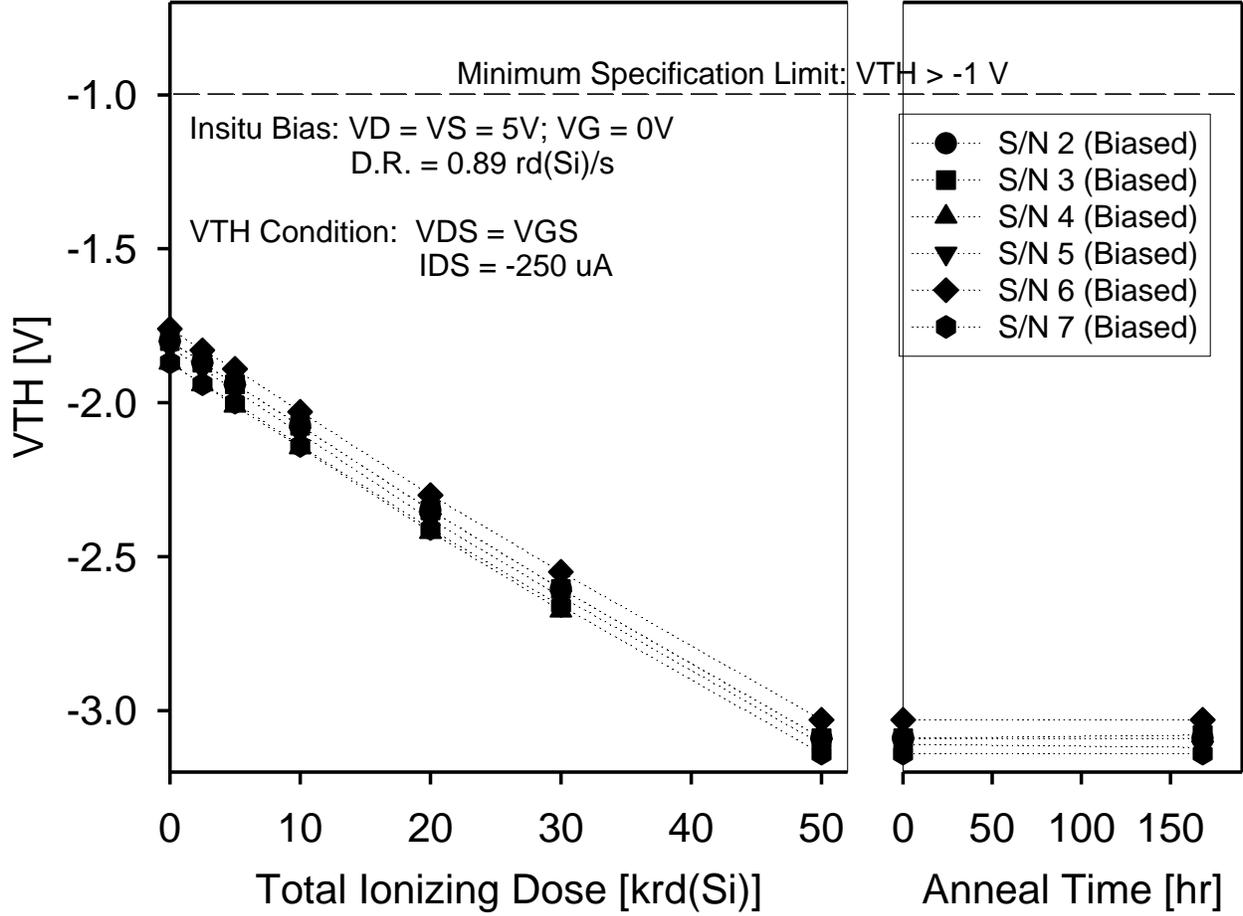

NAVSEA Crane Radiation Test Report

Report No: NSWC C6054-IRLML5103-0001

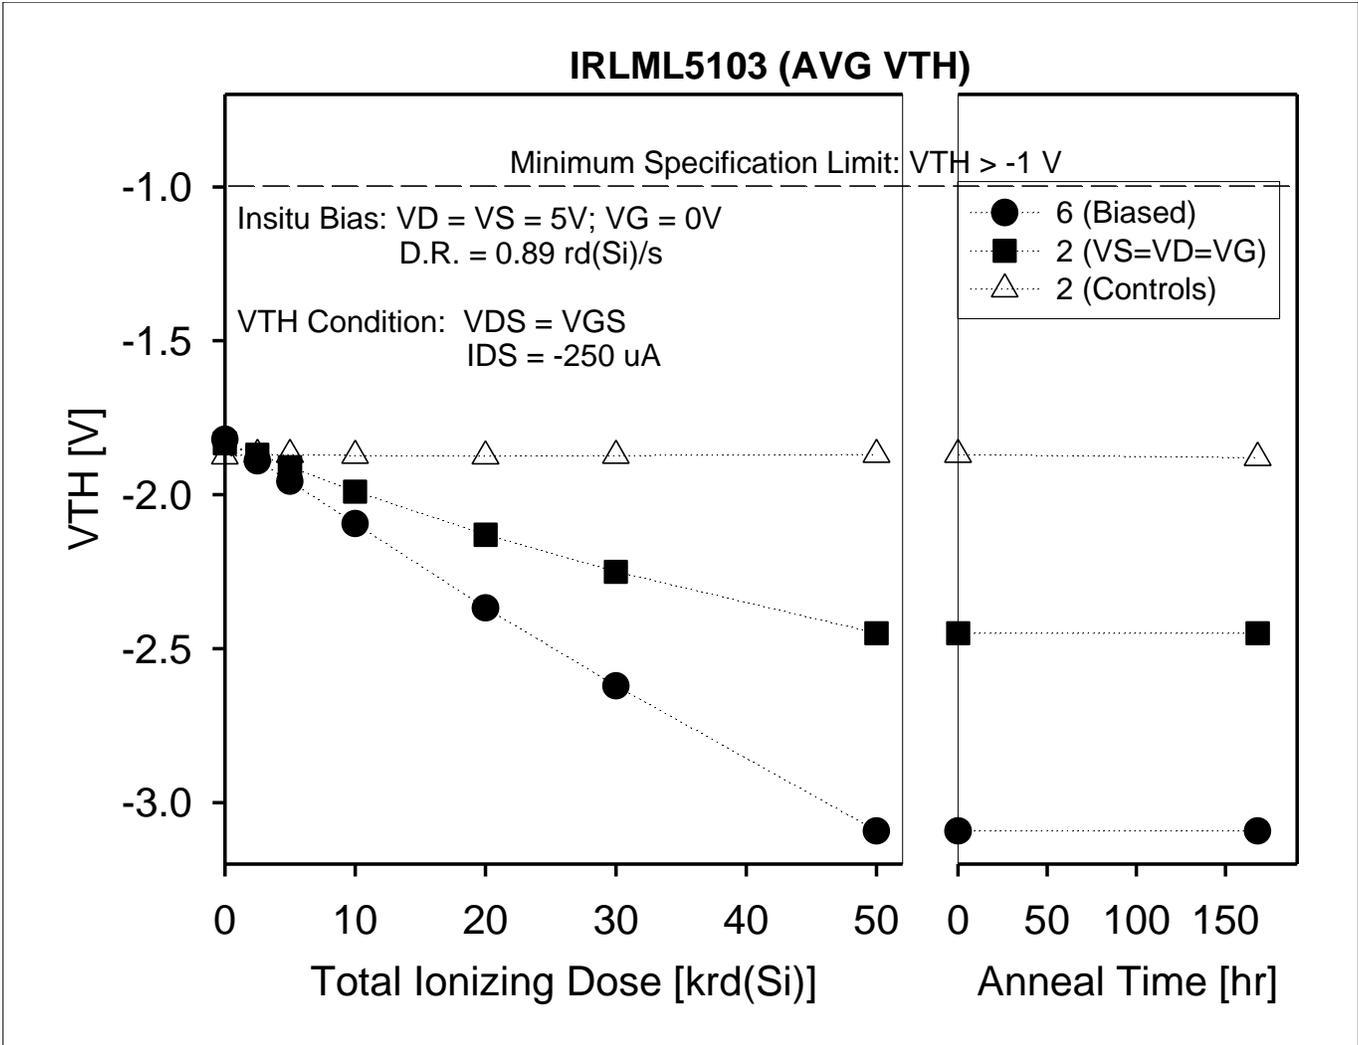

Prepared by:
Jeffrey L. Titus

Approved by:
Steve Clark